

This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses. It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

Classified according to EU Directive 1999/45/EC
For further information see our "Material Safety Data Sheets".

Edition 4, 09.2009

The latest revised edition of this brochure is the English version,
which is always published on our web site www.uddeholm.com



SS-EN ISO 9001
SS-EN ISO 14001

UDDEHOLM UNIMAX

The excellent properties offered enable Uddeholm Unimax to be used for many tooling applications. Reduced cycle time and longer tool life contributes to improve the overall economy. With an exceptional combination of high ductility and high hardness, Uddeholm Unimax is perfect when moulding plastic details and constructions that mean hard wear on the mould.

When choosing the right steel, a lot of parameters must be considered. The tool user wants to maximize the life and performance of the tool, minimizing the costs for production and down time. And in the end, it all boils down to the cost per part produced.

For the customers Uddeholm Unimax gives a lot of benefits:

- Excellent for reinforced plastic details, suitable for long run production and compression moulding. The combination of high ductility and high hardness means improved durability and wear resistance.
- Reduced cycle time – very good heat diffusion. Application tests have shown that Uddeholm Unimax has better dynamic heat conductivity than H13 type of steels, resulting in significantly reduced cycle times.
- Longer tool life, the property profile will increase the tool life substantially. High ductility helps prevent brittle fracture and will make the production run a lot smoother.
- Good surface treatment properties. The high hardness and toughness together with a good dimensional stability makes Uddeholm Unimax suitable as substrate steel for various surface-coatings.
- Very good hardenability which results in the same good properties throughout the entire cross-section. Large mould need high toughness and high resistance to indentations all the way through.

But it is not only within the plastic moulding segment Uddeholm Unimax is universal, but also within the entire tooling field. This means that Uddeholm Unimax is suitable to cope with applications found in severe cold work and hot work tooling. The excellent combination of toughness and hardness also makes it a universal engineering grade.

As we say; The harder, the better!

General

Uddeholm Unimax is a chromium-molybdenum-vanadium alloyed tool steel which is characterized by:

- Excellent toughness and ductility in all directions
- Good wear resistance
- Good dimensional stability at heat treatment and in service
- Excellent through-hardening properties
- Good resistance to tempering back
- Good hot strength
- Good thermal fatigue resistance
- Excellent polishability

Typical analysis %	C	Si	Mn	Cr	Mo	V
	0,5	0,2	0,5	5,0	2,3	0,5
Standard specification	None					
Delivery condition	Soft annealed to approx. 185 HB					
Colour code	Brown/grey					

Applications

Uddeholm Unimax is suitable for long run production moulds, moulds for reinforced plastics and compression moulding.

Uddeholm Unimax is a problem solver in severe cold work tooling applications such as heavy duty blanking, cold forging and thread rolling, where high chipping resistance is required.

Engineering and hot work applications requiring high hardness and toughness are also an option.

Properties

The properties below are representative of samples which have been taken from the centre of bars with dimensions 396 x 136 mm (15,6" x 5,35"), Ø 125 mm (4,93") and Ø 220 mm (8,67"). Unless otherwise indicated all specimens have been hardened at 1025°C (1875°F), gas quenched in a vacuum furnace and tempered twice at 525°C (975°F) for two hours; yielding a working hardness of 56–58 HRC.

Physical properties

Hardened and tempered to 56–58 HRC

Temperature	20°C (68°F)	200°C (390°F)	400°C (750°F)
Density, kg/m ³ lbs/in ³	7 790 0,281	–	–
Modulus of elasticity MPa psi	213 000 31,2 x 10 ⁶	192 000 27,8 x 10 ⁶	180 000 26,1 x 10 ⁶
Coefficient of thermal expansion per °C from 20°C per °F from 68°F	– –	11,5 x 10 ⁻⁶ 6,3 x 10 ⁻⁶	12,3 x 10 ⁻⁶ 6,8 x 10 ⁻⁶
Thermal conductivity W/m °C Btu in/(ft ² h°F)	– –	25 174	28 195
Specific heat j/kg°C Btu/lb°F	460 0,11	–	–


Mechanical properties

Approx. strength and ductility at room temperature at tensile testing.

Hardness	54 HRC	56 HRC	58 HRC
Yield strength, R _{p0,2}	1720 MPa	1780 MPa	1800 MPa
Tensile strength, R _m	2050 MPa	2150 MPa	2280 MPa
Elongation, A ₅	9 %	8 %	8 %
Reduction of area, Z	40 %	32 %	28 %


**APPROXIMATE STRENGTH
AT ELEVATED TEMPERATURES**

Longitudinal direction. The specimens were hardened from 1025°C (1875°F) and tempered twice at 525°C (975°F) to 58 HRC.

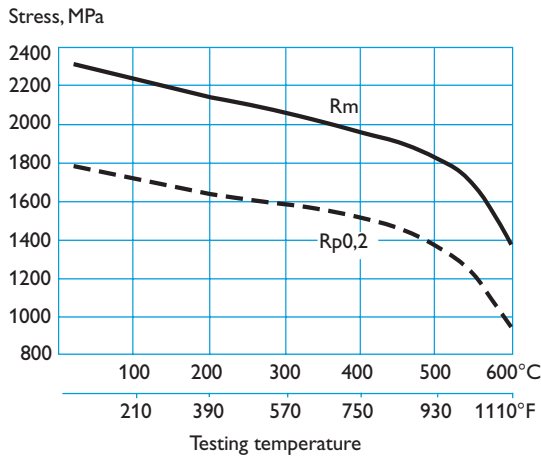


**EFFECT OF TIME AT
HIGH TEMPERATURES ON HARDNESS**

Initial hardness 57 HRC.

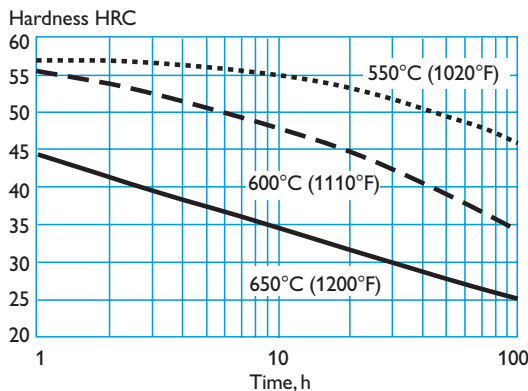

**EFFECT OF TESTING TEMPERATURE
ON IMPACT ENERGY**

Charpy-V specimens, longitudinal and short transverse direction. Approximate values for specimens from Ø 125 mm (4,9") bar.

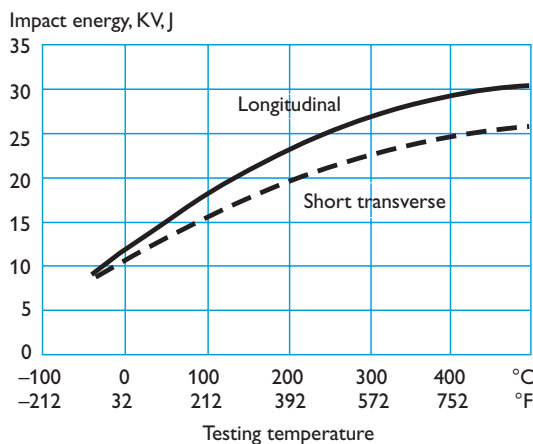

Heat treatment— general recommendations

Soft annealing

Protect the steel and heat through to 850°C (1560°F). Then cool in furnace at 10°C (20°F) per hour to 600°C (1110°F), then freely in air.

Stress relieving

After rough machining the tool should be heated through to 650°C (1200°F), holding time 2 hours. Cool slowly to 500°C (930°F), then freely in air.

Hardening

Preheating temperature: 600–650°C (1110–1200°F) and 850–900°C (1560–1650°F).

Austenitizing temperature: 1000–1025°C (1830–1875°F), normally 1025°C (1875°F).

Holding time: 30 minutes

Temperature		Soaking time minutes	Hardness before tempering
°C	°F		
1000	1830	30	61 HRC
1025	1875	30	63 HRC

Soaking time = time at hardening temperature after the tool is fully heated through.

Protect the tool against decarburization and oxidation during austenitizing.


Quenching media

- High speed gas/circulating atmosphere.
- Vacuum furnace (high speed gas with sufficient overpressure).
- Martempering bath, salt bath or fluidized bed at 500–550°C (930–1020°F).
- Martempering bath at 200–350°C (390–660°F).


Note: Temper the tool as soon as its temperature reaches 50–70°C (120–160°F).

CCT GRAPH

Austenitizing temperature 1025°C (1875°F). Holding time 30 minutes.

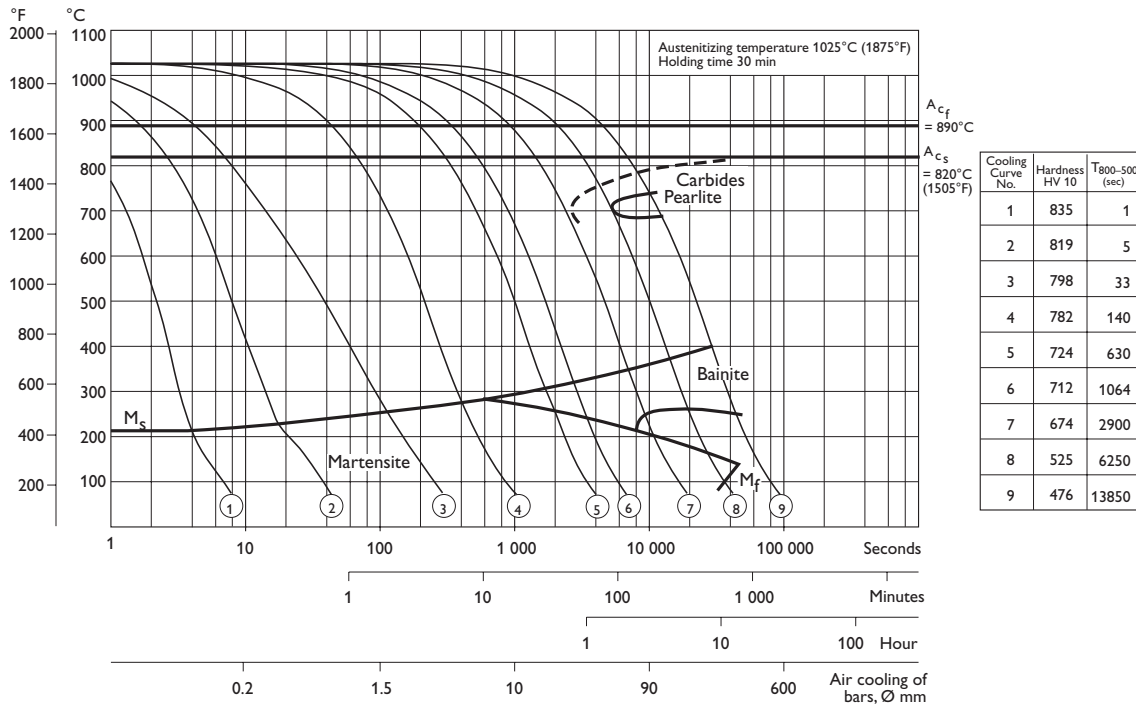


HARDNESS, GRAIN SIZE AND RETAINED AUSTENITE AS FUNCTIONS OF AUSTENITIZING TEMPERATURE

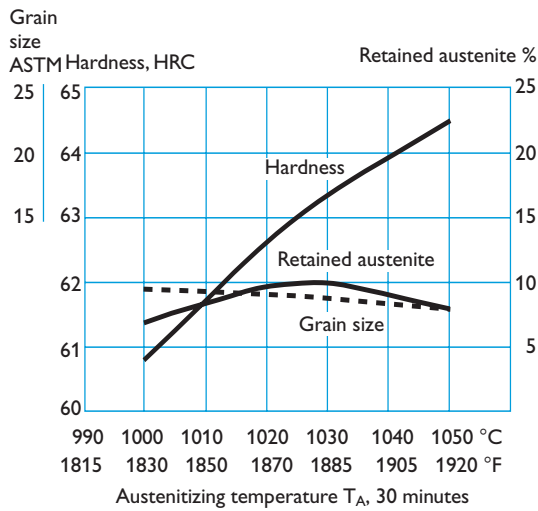

Tempering


Choose the tempering temperature according to the hardness required by reference to the tempering graph below. Temper at least twice with intermittent cooling to room temperature. The lowest tempering temperature which should be used is 525°C (980°F). The minimum holding time at temperature is 2 hours.

TEMPERING GRAPH

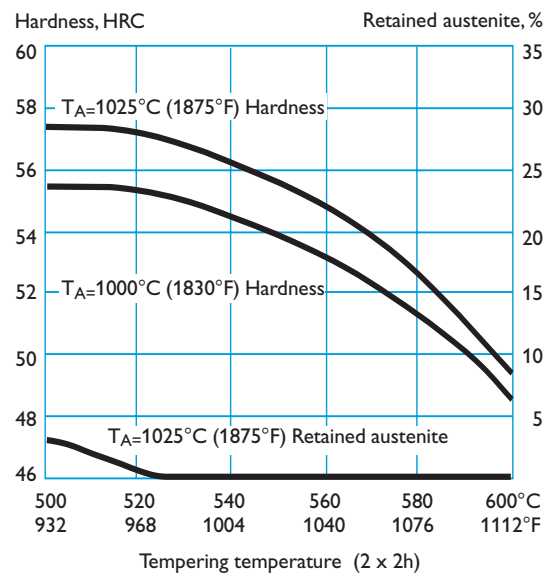

Dimensional changes during hardening and tempering

The dimensional changes have been measured after austenitizing at 1020°C/30 minutes (1870°F/30 minutes) followed by gas quenching in N₂ at a cooling rate of 1,1°C/second between 800–500°C (1470–930°F) in a cold chamber vacuum furnace. Specimen size: 100 x 100 x 100 mm (3,9" x 3,9" x 3,9").

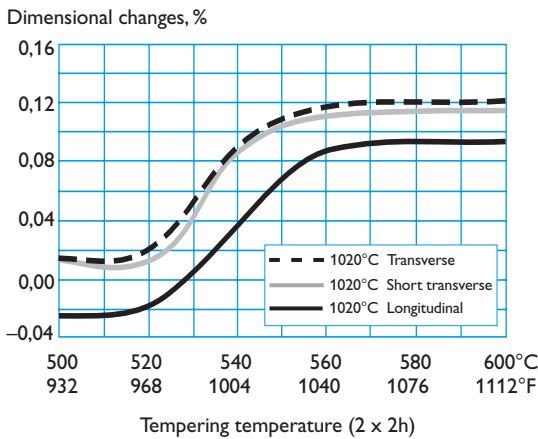

Surface treatments

Tool steels may be given a surface treatment in order to reduce friction and increase wear resistance. The most commonly used treatments are nitriding and surface coating with wear resistant layers produced via PVD or CVD.

The high hardness and toughness together with a good dimensional stability makes Uddeholm Unimax suitable as a substrate steel for various surface coatings.

Nitriding and nitrocarburizing

Nitriding and nitrocarburizing result in a hard surface layer which is very resistant to wear and galling.

The surface hardness after nitriding is approximately 1000–1200 HV_{0,2kg}. The thickness of the layer should be chosen to suit the application in question.

PVD

Physical vapour deposition, PVD, is a method for applying wear-resistant surface coating at temperatures between 200–500°C (390–930°F).

CVD

Chemical vapour deposition, CVD, is a method for applying wear-resistant surface coating at a temperature of around 1000°C (1830°F).

Cutting data recommendations

The cutting data below are to be considered as guiding values which must be adapted to existing local conditions.

The recommendations in following tables are valid for Uddeholm Unimax in soft annealed condition ~185 HB

Turning

Cutting data parameters	Turning with carbide		Turning with high speed steel Fine turning
	Rough turning	Fine turning	
Cutting speed (v _c) m/min f.p.m.	150–200 490–660	200–250 660–820	15–20 50–65
Feed (f) mm/r i.p.r.	0,2–0,4 0,008–0,016	0,05–0,2 0,002–0,008	0,05–0,3 0,002–0,012
Depth of cut (a _p) mm inch	2–4 0,08–0,16	0,5–2 0,02–0,08	0,5–2 0,02–0,08
Carbide designation ISO US	P20–P30 C6–C5 Coated carbide	P10 C7 Coated carbide or cermet	– –

Milling

FACE- AND SQUARE SHOULDER MILLING

Cutting data parameters	Milling with carbide	
	Rough milling	Fine milling
Cutting speed (v _c) m/min f.p.m.	120–170 390–560	170–210 560–690
Feed (f _i) mm/tooth inch/tooth	0,2–0,4 0,008–0,016	0,1–0,2 0,004–0,008
Depth of cut (a _p) mm inch	2–4 0,08–0,16	0,5–2 0,02–0,08
Carbide designation ISO US	P20–P40 C6–C5 Coated carbide	P10 C7 Coated carbide or cermet

END MILLING

Cutting data parameters	Type of milling		
	Solid carbide	Carbide indexable insert	High speed steel
Cutting speed (v _c) m/min f.p.m.	120–150 390–490	110–150 360–490	20–25 ¹⁾ 66–80 ¹⁾
Feed (f _z) mm/tooth inch/tooth	0,01–0,20 ²⁾ 0,0004–0,008 ²⁾	0,06–0,20 ²⁾ 0,002–0,008 ²⁾	0,01–0,30 ²⁾ 0,0004–0,012 ²⁾
Carbide designation ISO US	–	P20–P30 C6–C5	– –

¹⁾ For coated HSS end mill v_c 35–40 m/min. (115–130 f.p.m.)

²⁾ Depending on radial depth of cut and cutter diameter

Electrical Discharge Machining—EDM

Following the EDM process, the applicable die surfaces are covered with a resolidified layer (white layer) and a rehardened and untempered layer, both of which are very brittle and hence detrimental to die performance.

If EDM is used the white layer must be completely removed mechanically by grinding or stoning. After finish-machining the tool should be given an additional temper at approx. 25°C (50°F) below the highest previous tempering temperature. Further information is given in the Uddeholm brochure “EDM of Tool Steel”.

Drilling

HIGH SPEED STEEL TWIST DRILL

Drill diameter		Cutting speed (v _c)		Feed (f)	
mm	inch	m/min	f.p.m.	mm/r	i.p.r.
– 5	–3/16	15–20*	49–66*	0,05–0,10	0,002–0,004
5–10	3/16–3/8	15–20*	49–66*	0,10–0,20	0,004–0,008
10–15	3/8–5/8	15–20*	49–66*	0,20–0,30	0,008–0,012
15–20	5/8–3/4	15–20*	49–66*	0,30–0,35	0,012–0,014

¹⁾ For coated HSS drill v_c ~35–40 m/min. (115–130 f.p.m.)

CARBIDE DRILL

Cutting data parameters	Type of drill		
	Indexable insert	Solid carbide	Brazed carbide ¹⁾
Cutting speed (v _c) m/min f.p.m.	180–220 590–720	120–150 390–490	60–90 195–295
Feed (f), mm/r i.p.r.	0,03–0,10 ²⁾ 0,001–0,004 ²⁾	0,10–0,25 ²⁾ 0,004–0,01 ²⁾	0,15–0,25 ²⁾ 0,006–0,01 ²⁾

¹⁾ Drill with internal cooling channels and brazed carbide tip

²⁾ Depending on drill diameter

Grinding

A general grinding wheel recommendation is given below. More information can be found in the Uddeholm publication “Grinding of Tool Steel”.

RECOMMENDED GRINDING WHEELS

Type of grinding	Soft annealed condition	Hardened condition
Face grinding straight wheel	A 46 HV	A 46 HV
Face grinding segments	A 24 GV	A 36 GV
Cylindrical grinding	A 46 LV	A 60 KV
Internal grinding	A 46 JV	A 60 IV
Profile grinding	A 100 LV	A 120 KV


Welding

Welding of die components can be performed, with acceptable results, as long as the proper precautions are taken during the preparation of the joint, the filler material selection, the preheating of the die, the controlled cooling of the die and the post weld heat treatment processes. The following guidelines summarize the most important welding process parameters. For more detailed information refer to Uddeholm’s “Welding of Tool Steel” brochure.

Welding method	TIG	MMA
Preheating temperature	200–250°C (390–480°F)	200–250°C (390–480°F)
Filler material	UTP ADUR600 UTP A73G2	UTP 67S UTP 73G2
Maximum interpass temperature	350°C (660°F)	350°C (660°F)
Post weld cooling	20–40°C/h (45–70°F/h) for the first two hours and then freely in air.	
Hardness after welding	54–60 HRC	55–58 HRC
<i>Post weld heat treatment</i>		
Hardened condition	Temper at 510°C (950°F) for 2 h.	
Soft annealed condition	Soft-anneal according to the “Heat treatment recommendations”.	

Further information

Please contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steels.

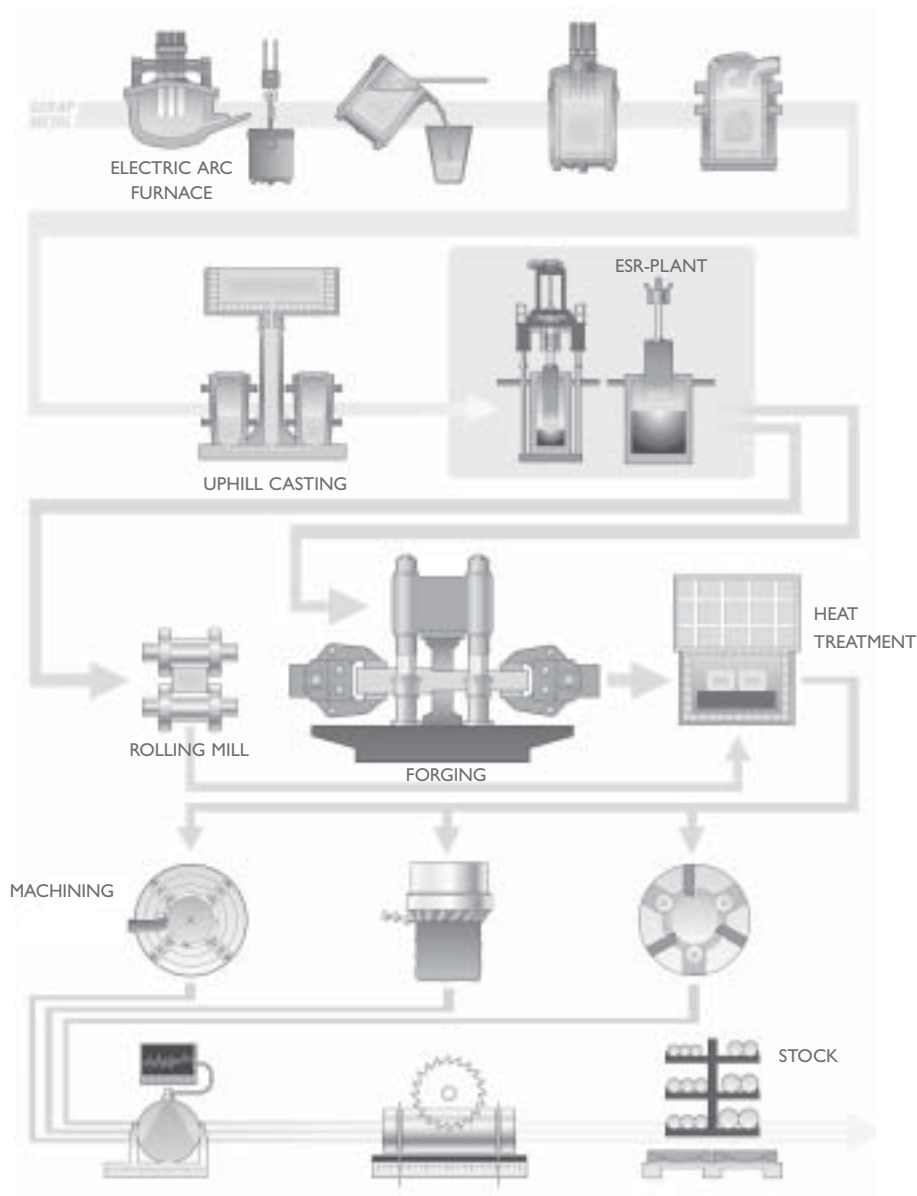

The ESR Tool Steel Process

The starting material for our tool steel is carefully selected from high quality recyclable steel. Together with ferroalloys and slag formers, the recyclable steel is melted in an electric arc furnace. The molten steel is then tapped into a ladle.

The de-slagging unit removes oxygen-rich slag and after the de-oxidation, alloying and heating of the steel bath are carried out in the ladle furnace. Vacuum de-gassing removes elements such as hydrogen, nitrogen and sulphur.

ESR PLANT

In uphill casting the prepared moulds are filled with a controlled flow of molten steel from the ladle.

From this, the steel can go directly to our rolling mill or to the forging press, but also to our ESR furnace where our most sophisticated steel grades are melted once again in an electro slag remelting process. This is done by melting a consumable electrode immersed in an overheated slag bath. Controlled solidification in the steel bath results in an ingot of high homogeneity, thereby

removing macro segregation. Melting under a protective atmosphere gives an even better steel cleanliness.

HOT WORKING

From the ESR plant, the steel goes to the rolling mill or to our forging press to be formed into round or flat bars.

Prior to delivery all of the different bar materials are subjected to a heat treatment operation, either as soft annealing or hardening and tempering. These operations provide the steel with the right balance between hardness and toughness.

MACHINING

Before the material is finished and put into stock, we also rough machine the bar profiles to required size and exact tolerances. In the lathe machining of large dimensions, the steel bar rotates against a stationary cutting tool. In peeling of smaller dimensions, the cutting tools revolve around the bar.

To safeguard our quality and guarantee the integrity of the tool steel we perform both surface- and ultrasonic inspections on all bars. We then remove the bar ends and any defects found during the inspection.



Network of excellence

UDDEHOLM is present on every continent. This ensures you high-quality Swedish tool steel and local support wherever you are. ASSAB is our wholly-owned subsidiary and exclusive sales channel, representing Uddeholm in various parts of the world. Together we secure our position as the world's leading supplier of tooling materials.

UDDEHOLM is the world's leading supplier of tooling materials. This is a position we have reached by improving our customers' everyday business. Long tradition combined with research and product development equips Uddeholm to solve any tooling problem that may arise. It is a challenging process, but the goal is clear – to be your number one partner and tool steel provider.

Our presence on every continent guarantees you the same high quality wherever you are. ASSAB is our wholly-owned subsidiary and exclusive sales channel, representing Uddeholm in various parts of the world. Together we secure our position as the world's leading supplier of tooling materials. We act worldwide, so there is always an Uddeholm or ASSAB representative close at hand to give local advice and support. For us it is all a matter of trust – in long-term partnerships as well as in developing new products. Trust is something you earn, every day.

For more information, please visit www.uddeholm.com, www.assab.com or your local website.

UD
WOR
RUST IS SOM
TRUST IS I
AUTOM
KINDING SU
TOUGHNESS STR
MATERIALS M
EDDING WATER
BYSTANDIN
RESULTS M
CUSTOMER B
SILITY TRUST IS
AUTOMOTIVE
LEADING SU
INNOVATION
STRENGTH INNOVATION
WORLDWIDE PRE
SOMETHING YO
PROBLEM
THE WORL
NOMY THE
DUCTILITY TO
COMMITMENT PART
KNOWLEDGE UP
KNOWLEDGE
RELIAB
OF EXCEL
AUTOMOTIVE A
ECONOMY THE
TOTAL ECONOMY
DUCTILITY TOUGHNE
HARDNESS WORLDW
TRUST IS SOMETH
UNDERSTANDING MACHIN
RESULTS SOLVING PROB
ECONOMY THE WORL
STRENGTH IN
TOUGHNESS STRENGTH I
MATERIALS PARTN
UNDERSTANDING MACHIN
SILITY RELIABILITY RESU
LASTING TOOLS TOTAL
YOU EARN, EVERY DAY. LO
OF THINKING HIGH PE
OFTOOLING MATERIALS C
INNOVATION KNOWLEDGE
STRENGTH INNOVATION KNOW
ESSENCE LONG DURABILITY
TRUST IS SOMETHING YOU EARN,
PROBLEMS AUTOMOTIVE